



ATT 2343 ESR

VPCAIM

SIMILAR STANDARDS

ATT 2343 ESR is similar to AISI H11, UNS T20811, DIN X38CrMoV5-1 and W.Nr. 1.2343, JIS SKD6. This steel is supplied in accordance with ASTM A681 and VDG M82.

GENERAL INFORMATION

ATT 2343 ESR is a hot work steel with high toughness in comparison with other steels for the same application, as AISI H13. This steel presents good thermal conductivity and an adequate response to nitriding and polishing.

MAIN CHARACTERISTICS

ATT 2343 ESR is a martensitic hot work steel intended to deliver high toughness associated with compatible mechanical resistance of AISI H13 steels. This steel is produced by ESR (Electro-Slag Remelting) process to assure high isotropy of mechanical properties; ATT 2343 ESR is commonly indicated for applications where the resistance to initiation and propagation of mechanical and thermal cracks are essential. In these situations, toughness is the most important property and determines the tool life.

CHEMICAL COMPOSITION

Typical Analysis (Weight Percent)

C	Si	Mn	Cr	Mo	V
0.40	1.00	0.35	5.00	1.30	0.50

STANDARD PRODUCTION RANGE

Production Route	Standard	Production Range	Finishing
Rolled Products	ASTM A681	Thickness between 8 to 152 mm with width between 25 to 320mm Round 5.50-152.40mm	Centerless ground Peeled Turned Milled
Forged Products		Round 152.40 - 760 mm Thickness up to 550mm with width up to 1000mm	Turned Peeled Milled

*Other dimensions and conditions are available upon inquiry.

DELIVERY CONDITION

ATT 2343 ESR is usually supplied in the annealed condition with a maximum hardness of 235HB. ATT 2343 ESR is also available in the hardened condition.

HEAT TREATMENT

Soft Annealing

Soft annealing is recommended to machining operations. For an spheroidized microstructure, heat slowly to a temperature between 845 and 900°C, soaking time of 2h controlled by the core followed by furnace cooling until 540°C and then air cooling to room temperature. The maximum hardness of ATT 2343 ESR steel will be 230HB.

Stress Relief

Stress relief heat treatment aims to reduce the residual stress of the part and it shall be employed after machining and before hardening. It shall be applied in dies with draws and profiles, in which the machining removal has been higher than 30%, in order to minimize distortions during and after hardening.

Heat slowly to 600-650°C followed by furnace cooling until 200°C. Stress relief for hardened parts must employ a temperature 50°C lower than that of the last tempering temperature.

Hardening

The austenitizing temperature should be between 950-1050°C and, once the temperature from the center to the surface is equal, keep the part 30 min for each inch of thickness in the austenitizing temperature. For better toughness performance, it is indicated 995°C and for better heat resistance response 1025°C can be applied.

The choice of the ideal temperature should also consider aspects of design and finishing details of the parts.

After austenitization, the quenching can be performed in different quench media as:

- ⇒ Pressurized vacuum furnace with pressure higher than 5 bar
- ⇒ Oil between 40-70°C
- ⇒ Salt bath between 500-550°C
- ⇒ Air cooling

Tempering


Temper immediately after quenching, i.e. as soon as parts reaches 60°C. Double tempering, at least is recommended and after each tempering cycle, parts shall be slowly cooled to room temperature.

Tempering temperatures are generally between 550-650°C, depending upon the desired hardness. The time of each tempering cycle shall be at least 2 hours in temperature. Avoid temperature range between 450 and 540°C as it can promote an excessive loss in toughness.

For parts with thickness larger than 70 mm, the time at temperature should be calculated according to their size, being a reference for calculation about one hour for each inch of thickness.

Surface Treatments

Surface treatments as nitriding, PVD and CVD are recommended when higher values of surface hardness and high abrasion wear resistance are required. Surface treatments shall be employed after hardening and tempering, since their temperatures is at least 50°C lower than the last tempering heat treatments.

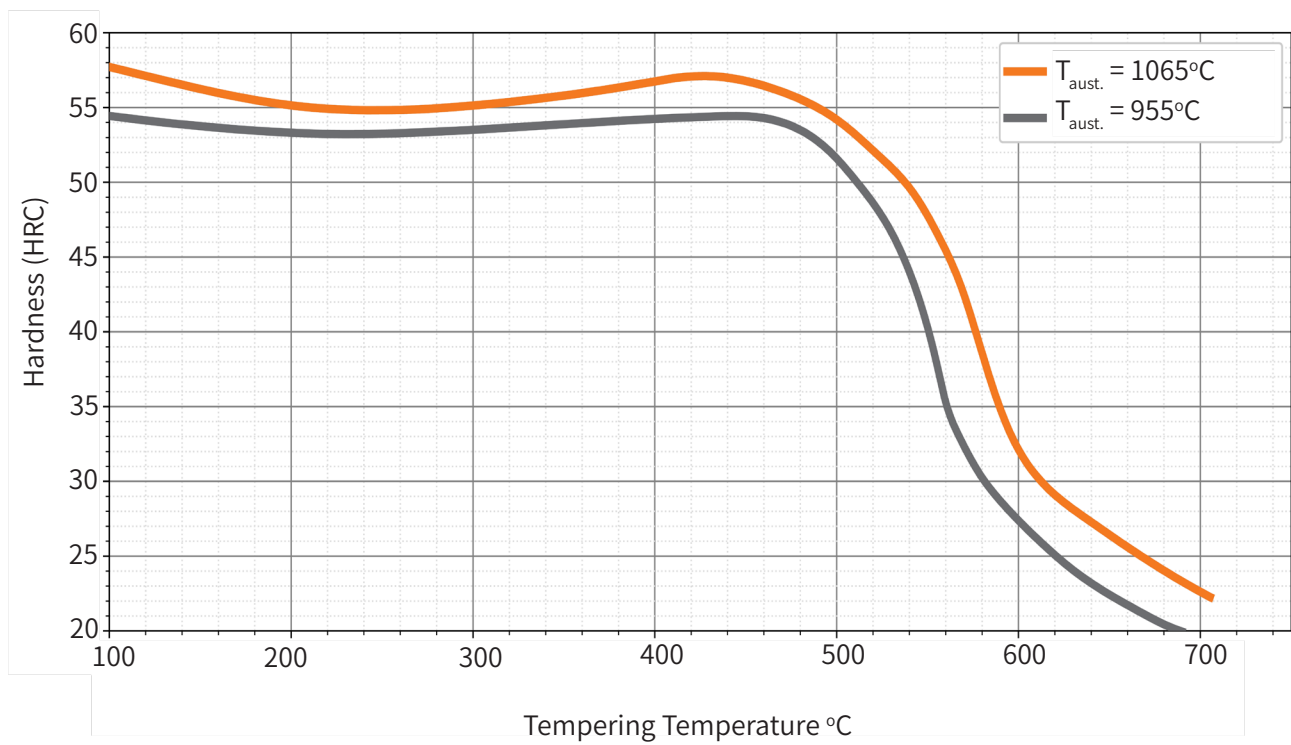

Tempering curve of ATT 2343 ESR after hardening at 980°C. Tempering time: 2 hours
Curve obtained from specimens with cross section of 20 mm x 20 mm

MAIN APPLICATIONS

ATT 2343 ESR main applications are:

- ⇒ Dies, tools and components for die casting and extrusion of aluminum alloys and other non-ferrous alloys, such as zinc, tin and lead
- ⇒ Inserts, shear blades and all types of dies for hot work that involves shock
- ⇒ Plastic molds with high polishing requirements.

MACHINABILITY

ATT 2343 ESR can be conventionally machined in the annealed condition. Care need to be taken in the selection of the tool and the speed to allow a good machinability. To avoid distortions on the part during hardening and tempering, it is recommended to perform a stress relief heat treatment before hardening, if more than 30% of part weight is removed in machining operations.

Electro-erosion process can be employed in heat treated dies or molds. After electro-erosion machining it is recommended to remove the superficial layer through fine grinding wheel. After grinding, it is recommended to perform a tempering heat treatment in temperature around 50°C lower than that of the last tempering.

WELDING

Welding is not recommended on ATT 2343 ESR. The Heat Affected Zones (HAZ), which will reduce the performance of the steel in the application. HAZ produced during arc welding operation are harder and brittle, with risk of cracking unless great care is exercised. In exceptional cases and always considering that, the welding would be a temporary solution ATT 2343 ESR might be welded using special procedures to minimize the HAZ.

The sequence of operations for repair welding ATT 2343 ESR depends upon its prior heat treatment. As a general guideline, it is recommended to: (a) preheat, (b) weld with appropriate filler metal, (c) perform a stress relief heat treatment, (d) machine, (e) quench and temper if in the annealed condition or stress relief if already hardened and (f) grind to final dimensions. The qualification of a specific welding procedure for repair is the key point to obtain the desired quality. The skill and experience of the welder is also a vital factor in obtaining satisfactory results.

IMPROVEMENT OF TOOL LIFE

Before starting operation, pre-heat slowly between 200-300°C, to obtain thermal homogenization of core and surface. Periodic stress relieving during the use of tools is recommended to improve the tool life.

MECHANICAL PROPERTIES

Typical Tensile Properties

Temperature		Ultimate Tensile Strength		Yield Strength		Elongation in 4D	Reduction of Area
°C	°F	MPa	ksi	MPa	ksi	%	%
20	68	1806	262	1482	215	10	35.8
150	300	1689	245	1358	197	10.1	36.1
425	800	1510	219	1289	187	11.4	38.7
540	1000	1241	180	965	140	11.0	35.4
650	1200	586	85	434	63	18.9	66.6

ATT 2343 ESR after quenching from 1010°C in air and double tempered at 570°C for 2h with air cooling. Hardness of 50HRC.

PHYSICAL PROPERTIES

Density

Temperature	g/cm ³	lb/in ³
20°C (68°F)	7.81	0.282

Thermal Conductivity

Temperature	W/(m · K)	Btu.in/(h.ft ² .°F)
100°C (212°F)	23.0	159
350°C (662°F)	28.4	196
400°C (752°F)	33.4	231
675°C (1247°F)	30.1	208

Thermal Expansion Coefficient

Temperature 20 °C to (68°F to)	J/kg.K	Btu/lb.°F
100°C (212°F)	10.5	5.8
200°C (392°F)	10.7	5.9
300°C (572°F)	11.0	6.1
400°C (752°F)	11.3	6.3
500°C (932°F)	11.7	6.5
600°C (1112°F)	12.1	6.7

The information contained herein is intended to provide general knowledge on our products and their uses. It should not be construed as a warranty of specific properties of the products described, or a warranty for fitness for a particular purpose. Each user of products from Advanced Tooling Tek (Shanghai) Co Ltd ("ATT") is responsible for making its own determination as to the suitability of ATT's products and services.



Advanced Tooling Tek (Shanghai) Co. Ltd. (ATT), established in 2001, is a trusted supplier of premium mold steel for China's manufacturing sector. With more than two decades of industry experience, ATT has built a strong reputation for reliability, technical expertise and customer-focused service.

Serving a wide range of industries, including automotive, electronics, home appliances and packaging, ATT offers a comprehensive portfolio of premium tool steels, including hot work tool steel, cold work tool steel and primarily plastic mold steel. To meet diverse customer requirements, ATT provide processing services such as sawing, milling, grinding, and heat treatment, ensuring efficient turnaround and consistent quality.

To further enhance its product range and technical strength, ATT collaborates closely with its group mill, Villares Metals. Headquartered in Sumaré, São Paulo, Brazil, Villares Metals has been a leader in specialty steels and alloys since 1944, supplying high-performance solutions to industries such as automotive, railway, energy, medical, oil and gas, aerospace and agriculture across the Americas and globally.

Through this collaboration, ATT offers customers access to world-class materials, international metallurgical expertise and innovative steel technologies. From mold manufacturers to component users and end product producers, ATT supports every stage of the value chain with dependable products, technical guidance and responsive service.

ATT is dedicated to being your preferred partner for high-performance tool steel solutions.

Advanced Tooling Tek (Shanghai) Co., Ltd.

Tel: +86 21 3373 8146 / +86 21 3373 8148

Email: info@att-metal.com

Address: 1F-A, 2F-A, No.1, Lane 499, Xin Miao San Rd., Xinqiao Town, Songjiang Dist.,
Shanghai China



Website



WeChat



信昌精密模具(上海)有限公司(ATT)成立于2001年,是为中国制造业提供优质模具钢的可靠供应商。凭借二十余年的行业经验,ATT以可靠性、技术专长和以客户为中心的服务建立了卓越声誉。

服务领域涵盖汽车、电子、家用电器及包装等众多行业,ATT提供全面的优质模具钢产品组合,包括热作模具钢、冷作模具钢及主要塑料模具钢。为满足多元化客户需求,ATT提供锯切、铣削、磨削及热处理等加工服务,确保高效周转与稳定品质。

为进一步拓展产品线与技术实力,信昌与集团旗下钢厂Villares Metals紧密协作。总部位于巴西圣保罗州苏马雷市的Villares Metals自1944年起便引领特种钢与合金领域,为美洲及全球汽车、铁路、能源、医疗、石油天然气、航空航天及农业等行业提供高性能解决方案。

通过此项合作,信昌为客户提供世界级材料、国际冶金专业知识及创新钢铁技术。从模具制造商到零部件用户及终端产品生产商,ATT以可靠产品、技术指导和响应式服务支持价值链的每个环节。

信昌致力于成为您首选的高性能工具钢解决方案合作伙伴。

信昌精密模具(上海)有限公司

电话: +86 21 3373 8146 / +86 21 3373 8148

邮箱: info@att-metal.com

地址: 上海市松江区新桥镇新庙三路499弄1号1层A区、2层A区, 邮编: 201612



信昌官网



信昌微信公众号